

## TEST REPORT

CUSTOMER NAME: Wixsteel Industrial International Trading Co.,Ltd.  
ADDRESS: /

The following sample(s) was/ were submitted and identified on behalf of the client as:

Sample Name : 14NiCr14  
Test Item : Chemical Composition Analysis; Tensile test  
Date of Receipt : 2019-01-07  
Testing Start Date : 2019-01-07  
Testing End Date : 2019-01-07  
Test result(s) : For further details, please refer to the following page(s)

\*\*\*\*\*To be continued\*\*\*\*\*

Signed for and on behalf of  
International Standard Quality  
Technology(Qingdao) Co., Ltd.

*Eve Wang*

*Roy Luo*

*Gmi Li*

Drafted by: Eve Wang

Checked By: Roy Luo

Authorized signatory: Gmi Li

本报告按本公司规定的通用服务条款编制发行，除非另有说明，本报告仅对来样负责，未经许可不得部分复制本报告。  
This test report is issued by the company subject to its general conditions of service. This test report refer only to the sample(s) tested unless otherwise stated. This test report cannot be reproduced, except in full, without prior written of the company.



## TEST REPORT

### 1. Chemical Composition Analysis:


Test Method: OES

Element	C	Mn	Cr	Ni
Result (wt), %	0.18	0.44	0.81	3.00

### 2. Tensile Test:

Test Method: EN ISO 6892-1:2016

Test item	Specimen	Result
Tensile strength ( $R_m$ ) (N/mm <sup>2</sup> )	Circular cross-section specimen	834
Proof strength ( $R_{p0.2}$ ) (N/mm <sup>2</sup> )		605
Elongation after fracture ( $A$ ) (%) $L_0=5.65\sqrt{S_0}$ (mm)		19.0

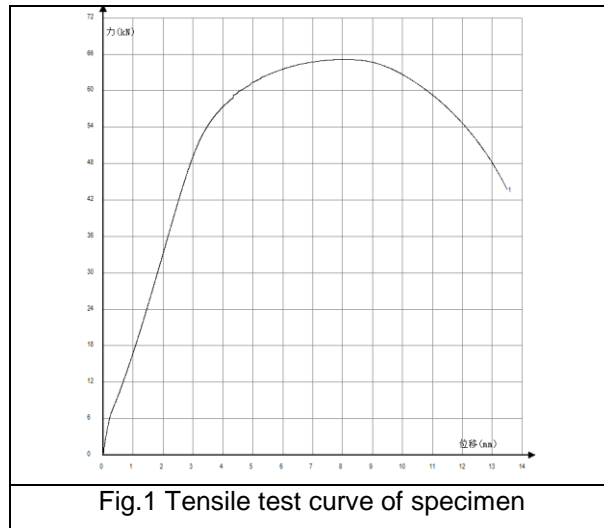

\*\*\*\*\*To be continued\*\*\*\*\*

本报告按本公司规定的通用服务条款编制发行，除非另有说明，本报告仅对来样负责，未经许可不得部分复制本报告。  
 This test report is issued by the company subject to its general conditions of service. This test report refer only to the sample(s) tested unless otherwise stated. This test report cannot be reproduced, except in full, without prior written of the company.

## TEST REPORT

Sample Photos:



\*\*\*\*\*End of report\*\*\*\*\*

本报告按本公司规定的通用服务条款编制发行，除非另有说明，本报告仅对来样负责，未经许可不得部分复制本报告。  
This test report is issued by the company subject to its general conditions of service. This test report refer only to the sample(s) tested unless otherwise stated. This test report cannot be reproduced, except in full, without prior written of the company.

